

HMT301



MITSUBISHI RAYON
CARBON FIBER & COMPOSITES

250-300°F (121-149°C) Cure Hot-melt Towpreg

Typical applications

Aerospace
Automotive
Marine
Industrial
Sporting goods

Out life

30 days at 70°F (21°C)

Shelf life

6 months at 40°F (4°C)
12 months at 0°F (-18°C)

Description

Newport-FTP® HMT301 is a 250-300°F (121-149°C) cure, hot melt towpreg, utilizing a toughened, controlled flow epoxy resin matrix. Versatile processing, excellent mechanical properties, and long out time make it suitable for a variety of applications including large scale structures where layup requirements can take days or weeks.

Benefits/features

- Stable bandwidth
- Easy de-spooling
- Moderate tack (adjustable)
- Excellent mechanical properties
- Compatible with many of MRCFAC 250-300°F (121-149°C) cure epoxy systems

Variants

- HMT301-D: Softer handling, particularly popular for filament winding

Application

With good toughness and impact resistance Newport-FTP® HMT301 is well suited for filament winding process and/or fiber placement process in variety of structural applications such as aerospace, marine, automotive, industrial and sporting goods markets.

Newport-FTP® HMT301 can be supplied on a wide range of standard, intermediate, and high modulus carbon, aramid, E-glass, and S-glass fibers.

Recommended processing conditions

Newport-FTP® HMT301 can be cured at temperatures from 250-300°F (121-149°C) depending on part size and complexity. Low, medium, and high pressure molding techniques may be used to cure HMT301 resin. Recommended cure cycle is 40 – 100 psi (345 – 690 kPa), 3°F/min (1.7°C/min) ramp to 275°F (135°C), hold for 60-90 minutes, cool to <140°F (60°C).

Technical Data Sheet

Neat resin [values are average and do not constitute a specification]

Property	Value
Gel time @ 275°F (135°C), minutes	4 – 7 minutes
Specific gravity	1.22
T _g (DMA, E'), °C (°F)	120 (248)

Mechanical data [values are average and do not constitute a specification]

34-700 12K 32%RC, autoclave cured, 40psi, 90 minutes at 275°F, normalized to 60%FV

Property	Test Method	RT
0° Tensile strength, ksi (MPa)	ASTM D3039	373 (2570)
0° Tensile modulus, Msi (GPa)		20.4 (140)
90° Tensile strength, ksi (MPa)		9.19 (63.4)
90° Tensile modulus, Msi (GPa)		1.26 (8.69)
0° Compressive strength, ksi (MPa)	ASTM D695mod	228 (1570)
0° Compressive modulus, Msi (GPa)		20.7 (142)
90° Compressive strength, ksi (MPa)		38.6 (266)
90° Compressive modulus, Msi (GPa)		1.45 (10.0)
0° Flexural strength, ksi (MPa)	ASTM D790	244 (1680)
0° Flexural modulus, Msi (GPa)		18.1 (124)
90° Flexural strength, ksi (MPa)		22.7 (156)
0° Short beam shear strength, ksi (MPa)	ASTM D2344	13.9 (95.8)

TR50S 12K 30%RC, autoclave cured, 80psi, 90 minutes at 275°F, normalized to 60%FV

Property	Test Method	RT
0° Tensile strength, ksi (MPa)	ASTM D3039	345 (2370)
0° Tensile modulus, Msi (GPa)		18.8 (129)
0° Compressive strength, ksi (MPa)	ASTM D695mod	213 (1460)
0° Compressive modulus, Msi (GPa)		17.8 (122)
0° Flexural strength, ksi (MPa)	ASTM D790	254 (1750)
0° Flexural modulus, Msi (GPa)		18.1 (124)
0° Short beam shear strength, ksi (MPa)	ASTM D2344	14.2 (97.0)

37-800 30K 27%RC, autoclave cured, 80psi, 90 minutes at 275°F, normalized to 60%FV


Property	Test Method	RT
0° Tensile strength, ksi (MPa)	ASTM D3039	355 (2440)
0° Tensile modulus, Msi (GPa)		23.0 (158)
0° Compressive strength, ksi (MPa)	ASTM D695mod	230 (1580)
0° Compressive modulus, Msi (GPa)		19.0 (131)
0° Flexural strength, ksi (MPa)	ASTM D790	250 (1720)
0° Flexural modulus, Msi (GPa)		20.0 (137)
0° Short beam shear strength, ksi (MPa)	ASTM D2344	14.8 (102)



MITSUBISHI RAYON
CARBON FIBER & COMPOSITES

Technical Data Sheet

Gel curve

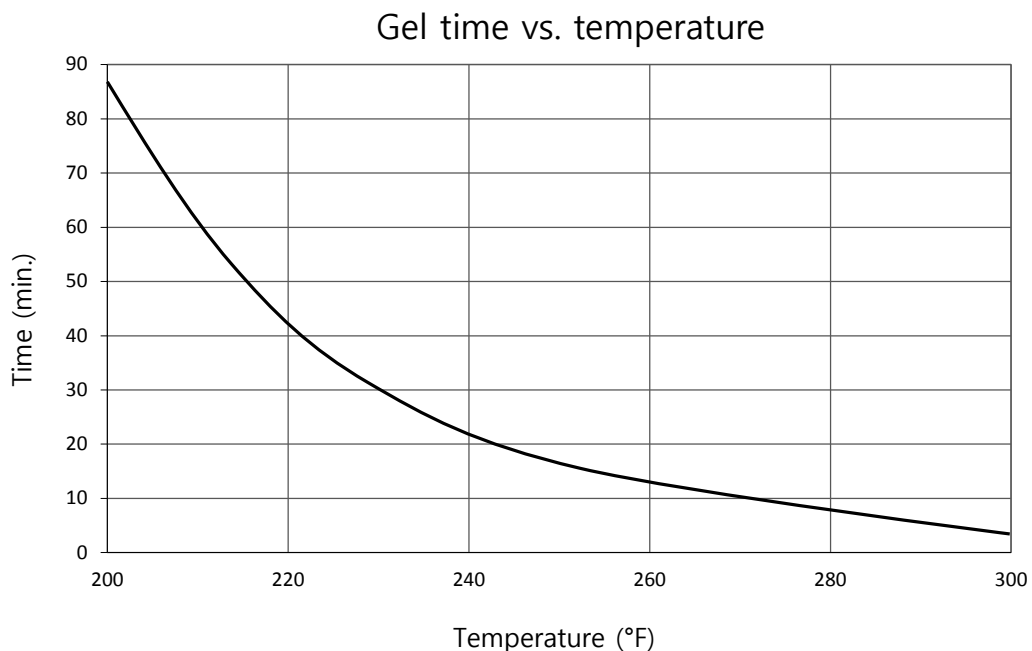

MITSUBISHI RAYON
CARBON FIBER & COMPOSITES

Technical Data Sheet

Newport-FTP® is a registered trademark of Mitsubishi Rayon Carbon Fiber & Composites

The information contained herein has been obtained under controlled laboratory conditions and are typical or average values and do not constitute a specification, guarantee, or warranty. Results may vary under different processing conditions or in combination with other materials. The data is believed to be reliable but all suggestions or recommendations for use are made without guarantee. You should thoroughly and independently evaluate materials for your planned application and determine suitability under your own processing conditions before commercialization. Furthermore, no suggestion for use or material supplied shall be considered a recommendation or inducement to violate any law or infringe any patent.

CORPORATE OFFICE
Composite Materials Div.
1822 Reynolds Ave.
Irvine, CA 92614

Tel: (949) 253-5680
Fax: (949) 253-5692
<http://www.mrcfac.com>
compositesales@mrcfac.com

THE KAITEKI COMPANY
Mitsubishi Chemical Holdings Group